

Client: Gabriel
Hjulgagervej 55
Postbox 59
DK-9100 Aalborg
Denmark

Entry No: 69483

Date received: 20/03/2015

Client's Description: Sample of fabric: Fame 66005 Dark Blue

TEST REPORT

Test Required: Flammability BS 5852 : 1979 Ignition sources 0 & 1

Pre-treatment: None

Conditioning: A minimum of 96 hours at 50 +/- 20% Relative Humidity, 20 +/- 5° C

Method of Test: BS 5852 : Part 1 : 1979

Date of Test: 09/04/2015

The following test results relate only to the ignitability of the combination of materials under the particular conditions of test; they are not intended as a means of assessing the full potential fire hazard of the materials in use.

Ignition Source	Observations	Result
0 (cigarette)	No flaming or progressive smouldering was observed within one hour of placement of the cigarettes.	PASS
1 (butane flame)	Flaming ceased within the specified two minute period after removal of the butane flame and no progressive smouldering occurred.	PASS

Note: A 20-22 kg/m³ non fire retardant polyurethane foam was used as the filling.

-----End of Page-----

This is hereby certified to be a correct return of the tests made of the items referred to herein.



D. Brockbank.
Materials Testing Manager
25th April 2015



- ❖ Unless instructed otherwise by the client sample remnants will be disposed of after 28 days
- ❖ Test marked (*) in this certificate are not included in the UKAS Accreditation Schedule for this Laboratory.
- ❖ Opinions and interpretations expressed herein are outside the scope of UKAS accreditation.
- ❖ This Certificate relates only to the sample received and, unless that sample has been drawn by the staff of this laboratory, or its agent, and endorsed accordingly, any application of the result to a bulk quantity or other material is entirely the responsibility of the client.



Client: Gabriel
Hjulgagervej 55
Postbox 59
DK-9100 Aalborg
Denmark


Entry No: 69483

During the tests the following data was recorded: -

	Source 0		Source 1	
Time of Ignition (sec)	No Ignition	No Ignition	15	14
Time to extinction of flame after removal of butane flame (sec)	N/A	N/A	1	1
Time of Cover Split (sec)	Did Not Split	Did Not Split	Did Not Split	Did Not Split
Melting (Yes or No)	No	No	No	No
Dripping (Yes or No)	No	No	No	No
Charring (Yes or No)	Yes	Yes	Yes	Yes

-----End of Document-----

This is hereby certified to be a correct return of the tests made of the items referred to herein.

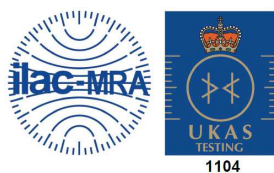


D. Brockbank.
Materials Testing Manager
25th April 2015

- ❖ Unless instructed otherwise by the client sample remnants will be disposed of after 28 days
- ❖ Test marked (*) in this certificate are not included in the UKAS Accreditation Schedule for this Laboratory.
- ❖ Opinions and interpretations expressed herein are outside the scope of UKAS accreditation.
- ❖ This Certificate relates only to the sample received and, unless that sample has been drawn by the staff of this laboratory, or its agent, and endorsed accordingly, any application of the result to a bulk quantity or other material is entirely the responsibility of the client.

